

NANO EXPRESS

Open Access



Alkali-metal-adsorbed g-GaN monolayer: ultralow work functions and optical properties

Zhen Cui^{1*} , Xia Wang³, Enling Li¹, Yingchun Ding², Changlong Sun⁴ and Minglei Sun^{5,6*}

Abstract

The electronic and optical properties of alkali-metal-adsorbed graphene-like gallium nitride (g-GaN) have been investigated using density functional theory. The results denote that alkali-metal-adsorbed g-GaN systems are stable compounds, with the most stable adsorption site being the center of the hexagonal ring. In addition, because of charge transfer from the alkali-metal atom to the host, the g-GaN layer shows clear n-type doping behavior. The adsorption of alkali metal atoms on g-GaN occurs via chemisorption. More importantly, the work function of g-GaN is substantially reduced following the adsorption of alkali-metal atoms. Specifically, the Cs-adsorbed g-GaN system shows an ultralow work function of 0.84 eV, which has great potential application in field-emission devices. In addition, the alkali-metal adsorption can lead to an increase in the static dielectric constant and extend the absorption spectrum of g-GaN.

Keywords: G-GaN, Adsorption, Work function, Field emission device, Optical properties, Density functional theory

Background

Compared with traditional semiconductor materials, three-dimensional GaN is a wide-bandgap semiconductor material [1]. As such, it can enable equipment operation at ultra-high voltage, frequency, or temperature and exhibits high luminous efficiency, good thermal conductivity, high temperature resistance, resistance to acids and alkalis, and anti-radiation properties. As an optoelectronic material, three-dimensional GaN has potential applications in laser printing and high-storage-density compact discs, potentially strongly influencing the technology of computer storage [2]. In recent years, two-dimensional (2D) materials have received extensive attention because of their fascinating optical, mechanical, electronic, and magnetic properties and potential for multifunctional applications [3–9]. 2D materials are far thinner than bulk materials, and the mechanical, electronic, thermal, and optical properties of such materials differ substantially from those of their bulk counterparts [10]. Specifically, 2D

GaN is a wide-bandgap material with enhanced optoelectronic performance. Very recently, it was synthesized via a migration-enhanced encapsulated growth technique [11].

Studying and understanding the interaction between atoms on solid surfaces is one of the basic scientific problems in the field of surface physics. Therefore, controlling such self-assembling structures is important for the development of nanodevices. Atoms adsorbed onto a solid surface can interact indirectly through electron scattering or elastic distortion of the substrate, with the long-range atomic interaction modulated by the substrate playing an important role in atomic self-assembly. Because alkali-metal atoms can easily lose electrons, the adsorption of alkali metals onto semiconductor materials can change them to n-type, which will in turn reduce their work function and change their optoelectronic properties [12]. In recent years, many research groups have reported studies of the optoelectronic properties of alkali-metal-adsorbed 2D materials [13–23]. For instance, Chan et al. [13] investigated the adsorption of alkali-metal atoms on graphene and discovered the reduction of work function of graphene. Jin et al. [14] and Qiao et al. [15] investigated the adsorption of alkali metals on graphene using first-principles method and

* Correspondence: zcui@xaut.edu.cn; mingleisun@outlook.com

¹School of Automation and Information Engineering, Xi'an University of Technology, Xi'an 710048, People's Republic of China

⁵School of Mechanical Engineering, Southeast University, Nanjing, Jiangsu 211189, People's Republic of China

Full list of author information is available at the end of the article

found that the optoelectronic properties of graphene are modified by the adsorption of alkali-metal. Many previous works investigated that the electronic and magnetic properties of adatom adsorptions on black and blue phosphorene, which found the surface adsorptions effectively functionalize the phosphorene system with versatile spintronic features [16–18]. However, the full photoelectric properties of alkali-metal-adsorbed g-GaN are still not clear.

In this article, the band structures, density of states, work functions, and optical properties of pristine g-GaN and alkali-metal-adsorbed g-GaN are elaborated; this research is potentially important for the fabrication of g-GaN-based field-emission and optoelectronic devices.

Methods

All the calculations are performed by using the Vienna Ab initio Simulation Package based on first-principles with density functional theory [24]. The generalized gradient approximation (GGA) in the form of the Perdew-Burke-Ernzerhof (PBE) functional [25] was adopted to describe the exchange-correlation interaction. The GGA-PBE method has been indicated to be very effective for surface research [26–29]. The kinetic cutoff energy for the plane-wave basis set is 500 eV. In the perpendicular direction of the g-GaN plane, the vacuum space was set to 20 Å. The Brillouin zone was described by a set of k -points in a $9 \times 9 \times 1$ grid using the Γ -centered scheme. All atoms are fully relaxed until the Hellmann–Feynman forces were less than 10^{-4} eV/Å and the total energy changes became less than 10^{-4} eV [29].

The adsorption energy for the alkali-metal-adsorbed g-GaN systems was calculated using the method of Cui et al. [12] According to the following equation:

$$E_{\text{ads}} = E_{\text{g-GaN-X}} - E_{\text{g-GaN}} - \mu_{\text{X}}, \quad (1)$$

where E_{ads} is the adsorption energy, $E_{\text{g-GaN}}$ and $E_{\text{g-GaN-X}}$ denote the total energy of pristine g-GaN before and after alkali-metal adsorption, respectively, and μ_{X} is the chemical potential of a single alkali-metal atom. Based on this equation, a negative value of E_{ads} denotes a stable structure.

The charge-density difference is described as

$$\Delta\rho = \rho_{\text{T}} - \rho_{\text{g}} - \rho_{\text{x}}, \quad (2)$$

where ρ_{T} , ρ_{g} , and ρ_{x} are the total charge on the alkali-metal-adsorbed g-GaN, pristine g-GaN, and adsorption atom, respectively.

Results and discussions

Figure 1 shows the model of g-GaN for four different adsorption sites; the T_{N} site is directly above the N atom, the T_{Ga} site is directly above the Ga atom, the T_{B} site is

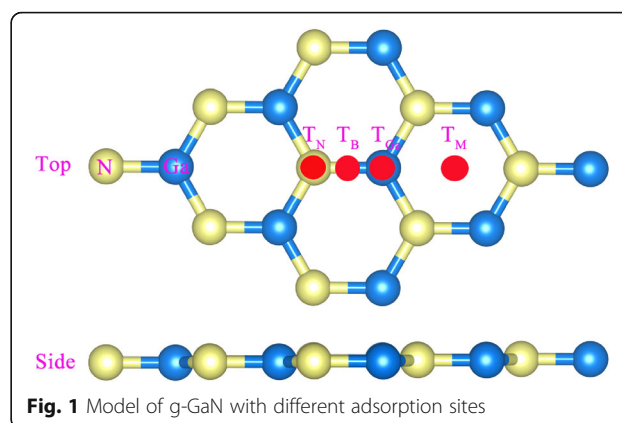


Fig. 1 Model of g-GaN with different adsorption sites

above the middle of the N-Ga bond, and the T_{M} site is above the center of a hexagon. The calculated E_{ads} of alkali-metal-adsorbed g-GaN is shown in Table 1. All the E_{ads} of different sites are negative, which demonstrates that the procedure of alkali-metal adsorption on g-GaN is exothermic and all the adsorption systems are stable. These results are similar to those obtained for alkali-metal-adsorbed GaN nanowires [12]. Moreover, the calculated results indicate that the most stable position is the T_{M} site; thus, the following discussions only concern the T_{M} adsorption site.

The lattice parameters of pristine and alkali-metal-adsorbed g-GaN are shown in Table 2. The lattice parameters of pristine g-GaN are 3.254 Å, which are in good agreement with previous results [30–33]. Furthermore, the lattice parameters of Li- or Na-adsorbed g-GaN are little smaller than that in pristine g-GaN, whereas the K-, Rb-, and Cs-adsorbed g-GaN are bigger than that in pristine g-GaN. Interestingly, as the atomic number of alkali metal atoms tunes larger, the lattice parameters of alkali-metal-adsorbed g-GaN increase. The bond lengths of the N-X or Ga-X are displayed in Table 2. The bond lengths of the N-X or Ga-X increase with the increasing of atomic number of alkali metal atoms. The adsorption height of alkali-metal-adsorbed g-GaN are shown in Table 2, which indicate that the adsorption height increase with the increasing of atomic number of alkali metal atoms.

Table 1 The adsorption energy for alkali-metal-adsorbed g-GaN with different sites

Adsorption style	$E_{\text{ads},T_{\text{Ga}}}$ (eV)	$E_{\text{ads},T_{\text{B}}}$ (eV)	$E_{\text{ads},T_{\text{N}}}$ (eV)	$E_{\text{ads},T_{\text{M}}}$ (eV)
Li	−1.89	−1.90	−1.26	−1.92
Na	−1.07	−1.12	−0.76	−1.18
K	−1.07	−1.09	−0.81	−1.21
Rb	−0.94	−0.98	−0.77	−1.07
Cs	−0.94	−1.03	−0.71	−1.08

Table 2 The lattice parameters, bond length, and adsorption height of pristine and alkali-metal-adsorbed g-GaN

Atom	Pristine	Li	Na	K	Rb	Cs
$d_{\text{N-X}}$ (Å)	/	2.154	2.511	2.917	3.084	3.249
$d_{\text{Ga-X}}$ (Å)	/	2.635	2.975	3.371	3.530	3.701
Lattice parameters	3.254	3.241	3.253	3.259	3.261	3.268
Adsorption height (Å)	/	2.501	2.718	3.102	3.335	3.598

The band structures of pristine and alkali-metal-adsorbed g-GaN are shown in Fig. 2. Figure 2a clearly shows that the band structure of pristine g-GaN exhibits semiconducting character, with a bandgap of 2.1 eV. This result is in good agreement with the previous reports [30–33]. However, the band structures for alkali-metal-adsorbed g-GaN show that the Fermi levels have entered the conduction band, as shown in Fig. 2b–f; thus, the alkali-metal-adsorbed g-GaN

system features a metallized character, with a gap appearing at approximately -1.8 eV under the Fermi level, and the gap of alkali-metal-adsorbed g-GaN is approximately 1.92 eV. Furthermore, the g-GaN is transformed into an n-type semiconductor after adsorption of the alkali metals because of the tendency for the alkali metals to lose electrons, resulting in an upshift of the Fermi level inside the conduction band.

The total density of states (TDOS) and partial density of states (PDOS) of pristine and alkali-metal-adsorbed g-GaN are shown in Fig. 3. In Fig. 3a, the TDOS of pristine g-GaN demonstrates that it is a semiconductor, consistent with the result of band structure. The PDOS calculations show that the valence-band maximum for pristine g-GaN originates from the N-2p and Ga-4p orbitals, in agreement with the previous results [34, 35]. To understand the electron states near the Fermi level, we


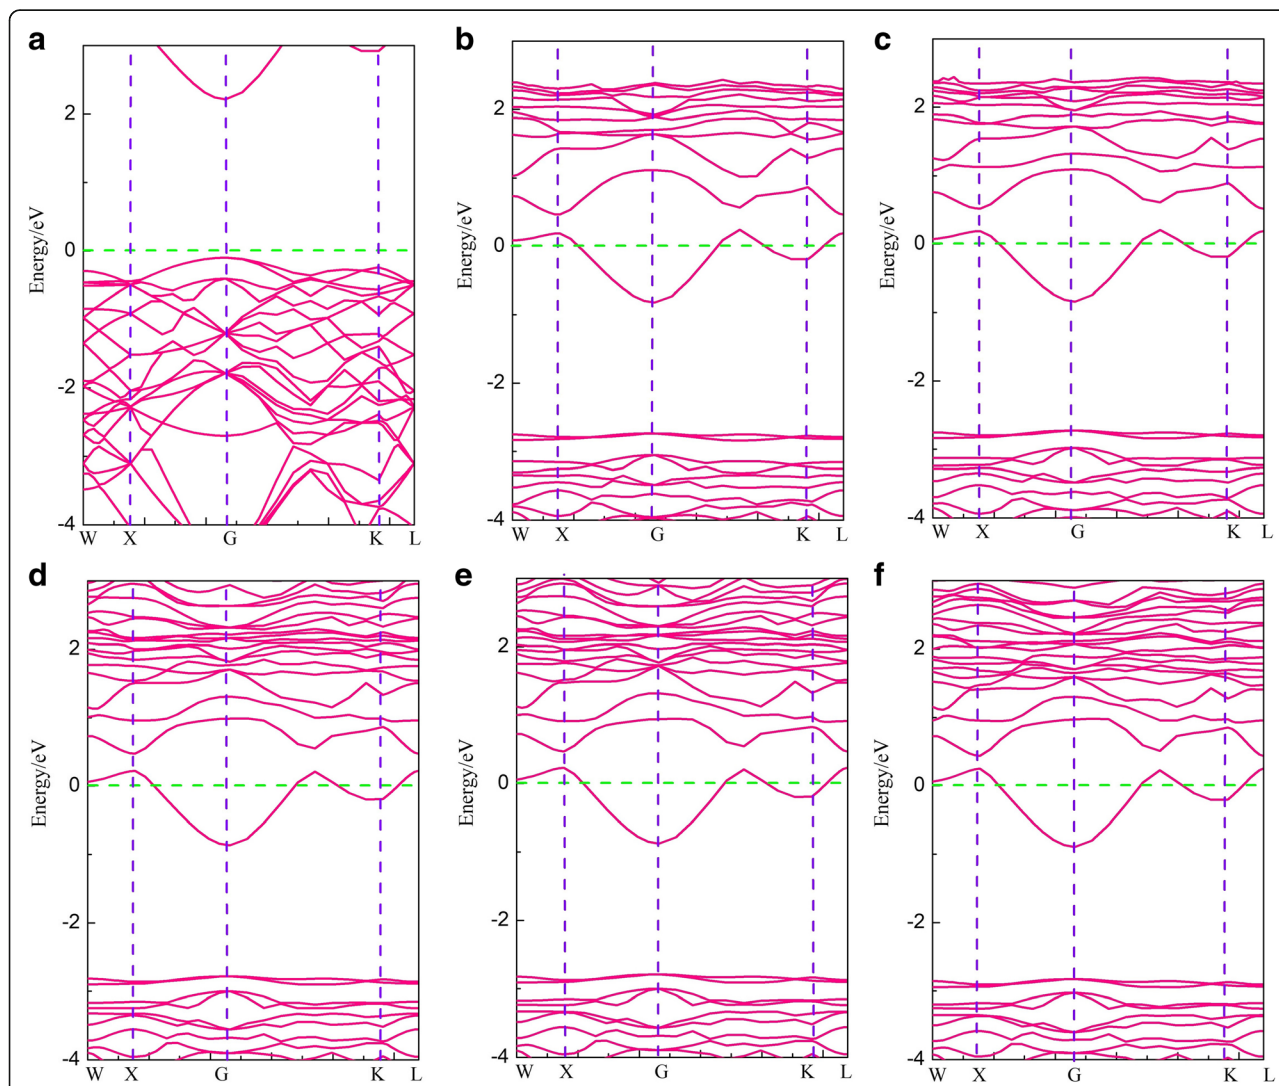


Fig. 2 Band structures for pristine and alkali-metal-adsorbed g-GaN: **a** pristine g-GaN, **b** Li-adsorbed g-GaN, **c** Na-adsorbed g-GaN, **d** K-adsorbed g-GaN, **e** Rb-adsorbed g-GaN, and **f** Cs-adsorbed g-GaN. The Fermi level is denoted by green dashed lines

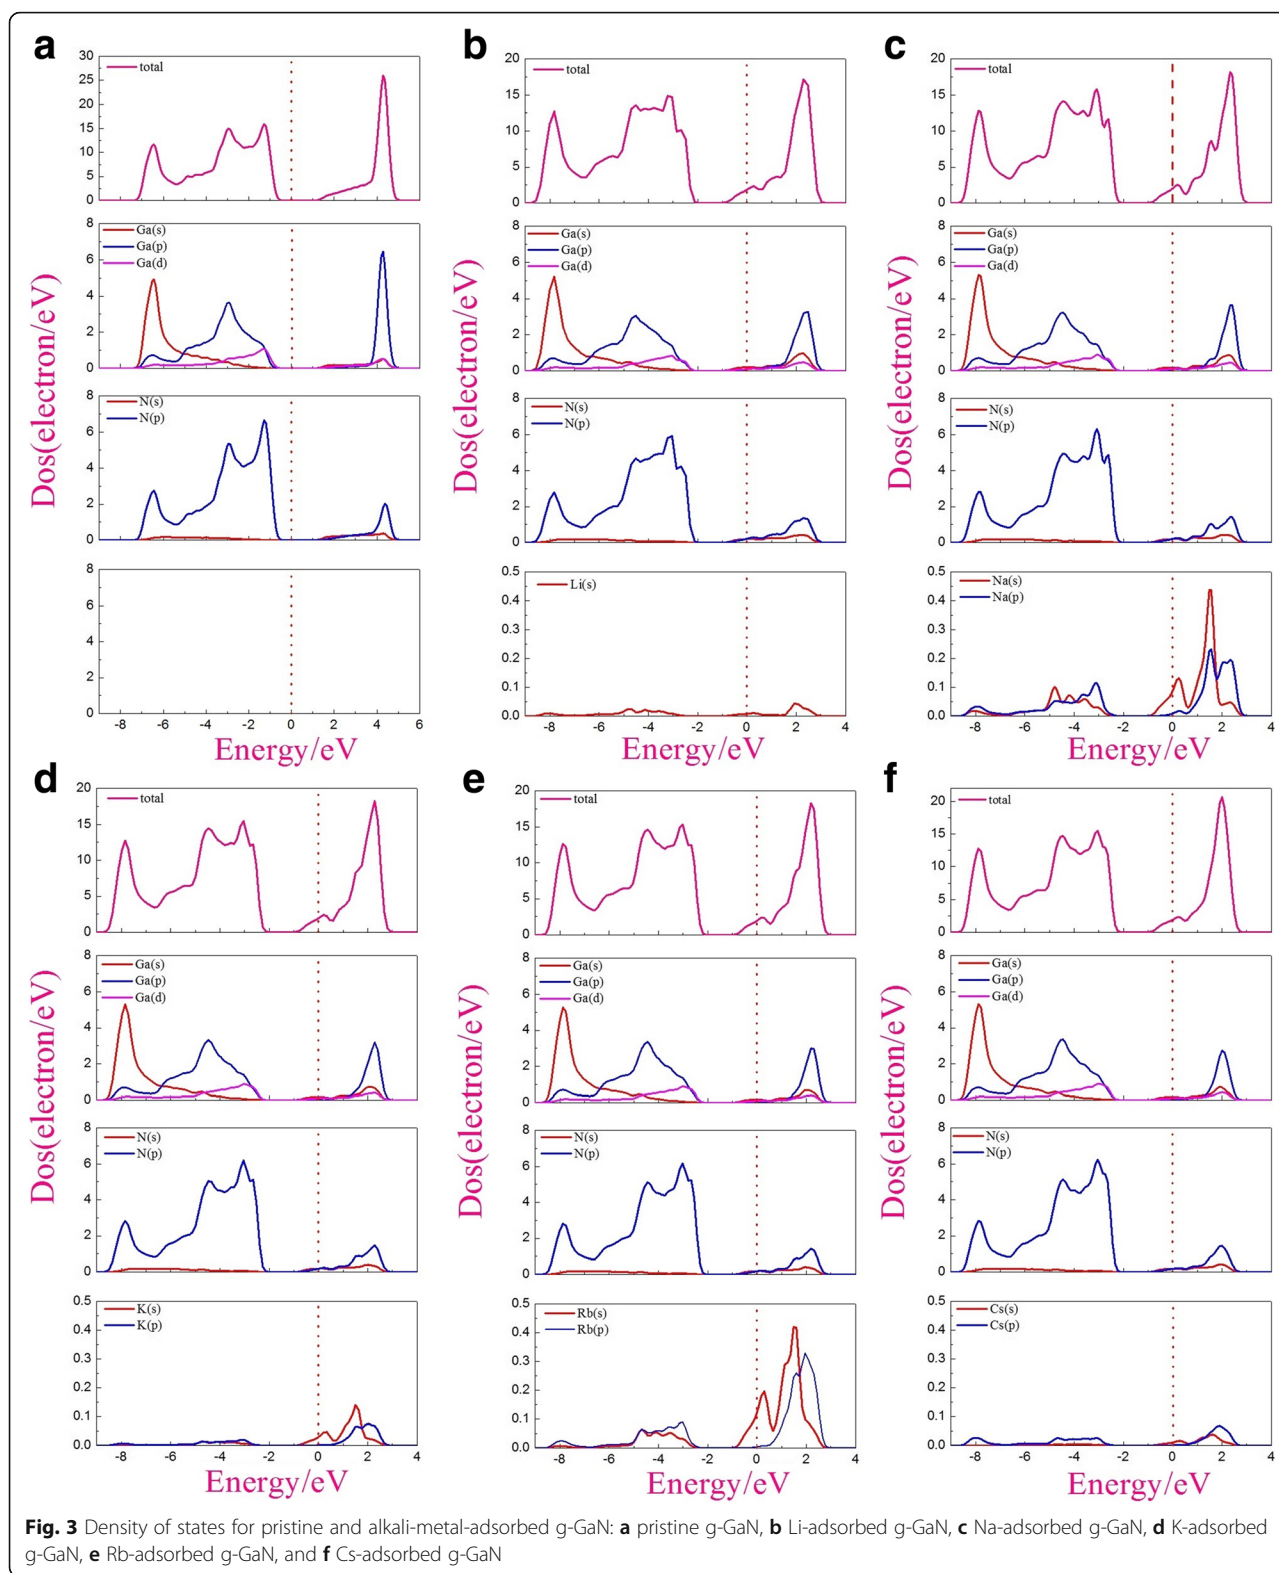

calculated the PDOS of alkali-metal-adsorbed g-GaN. As can be seen from Fig. 3b–f, the electron states near the Fermi level are mainly governed by the Ga-4s, N-2p, and 2s orbitals of the alkali metals.

Charge transfer is an important aspect of the adsorption system. The charge-density difference with an isosurface value of $0.002 \text{ e}/\text{\AA}^3$ for alkali-metal-adsorbed g-GaN is shown in Fig. 4. Interestingly, the electron

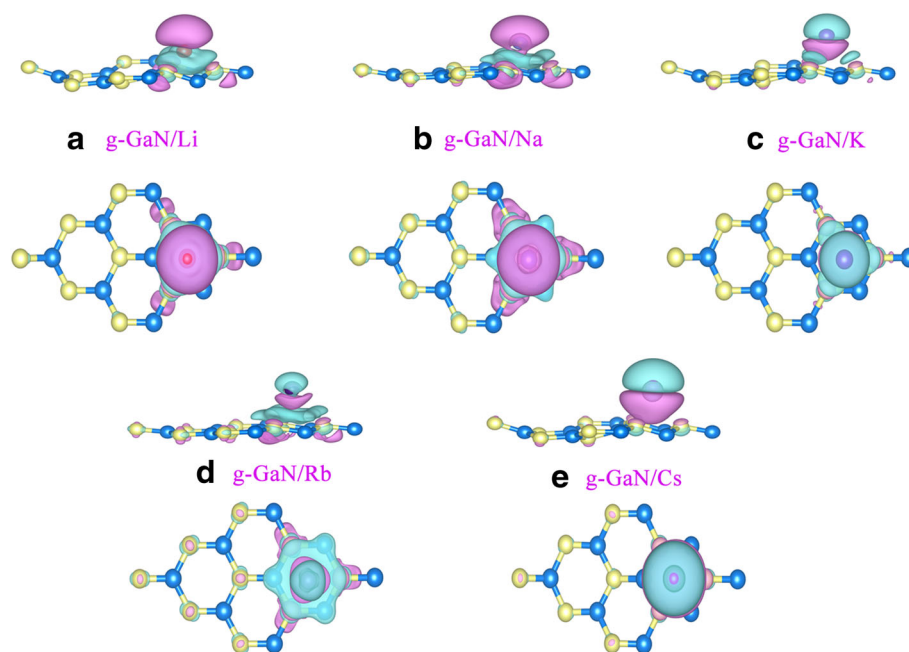



Fig. 4 The charge-density difference for alkali-metal-adsorbed g-GaN. **a** g-GaN/Li, **b** g-GaN/Na, **c** g-GaN/K, **d** g-GaN/Rb, **e** g-GaN/Cs. The magenta and cyan regions denote the gain and loss of electrons, respectively. The value of the isosurface is set to $0.002 \text{ e}/\text{\AA}^3$

distributions lie between all the alkali-metal atoms and the three under-coordinated N atoms. Therefore, alkali-metal-adsorbed g-GaN is formed by chemisorption. In addition, the large cyan region localized on alkali-metal atom suggests a large transfer from alkali-metal atom to g-GaN. Bader charge analysis shows that there are about $0.8833|e|$, $0.7803|e|$, $0.7997|e|$, $0.7905|e|$, $0.7936|e|$ transfer from Li, Na, K, Rb, Cs to g-GaN. Thus, all the results above confirmed the picture that the interactions in alkali-metal-adsorbed g-GaN are ionic bonding.

Work function is a critical factor for balancing the optoelectronic properties of materials. The work function of materials is equal to the vacuum level deduced from the Fermi level. To reveal intriguing feasibility, we studied tuning of the work function of g-GaN by alkali-metal adsorption. Figure 5 shows the work function schematic of pristine g-GaN and alkali-metal-adsorbed g-GaN. The work function of pristine g-GaN is 4.21 eV, which is slightly larger than that of GaN nanowires [12]. The work functions are 2.47, 1.88, 1.49, 1.29, and 0.84 eV for Li-, Na-, K-, Rb-, and Cs-adsorbed g-GaN, respectively; thus, the work function of g-GaN is substantially reduced following adsorption of an alkali metal adatom. Furthermore, the work functions of alkali-metal-adsorbed g-GaN are lower than those of alkali-metal-adsorbed GaN nanowires [12]. The main reason may due to the structure difference between GaN monolayer and nanowires. Moreover, the decreased work function demonstrates that the alkali-metal-adsorbed g-GaN can be used to field-emission devices.



Next, we turn to investigate the effect of the adsorption of alkali metal on the optical properties of g-GaN. Optical properties of materials can be depicted by the real part $\varepsilon_1(\omega)$ and imaginary part $\varepsilon_2(\omega)$ of the dielectric function, absorption $a(\omega)$, refractive $n(\omega)$, reflectivity $R(\omega)$, energy-loss function $L(\omega)$, and the extinction coefficient spectra $K(\omega)$, as reported previously [36–40]. The real part $\varepsilon_1(\omega)$ as a function of ω for pristine and alkali-metal-adsorbed g-GaN is shown in Fig. 6a. The $\varepsilon_1(0)$ of pristine g-GaN is 1.48, and the $\varepsilon_1(0)$ of alkali-metal-adsorbed g-GaN is 2.33 (Li), 3.13 (Na), 3.56 (K), 3.81 (Rb), and 3.81 (Cs). The data show that the $\varepsilon_1(0)$ of alkali-metal-adsorbed g-GaN is greater than that of pristine g-GaN; thus, the optical properties of g-GaN are highly sensitive and tunable. In addition, when the energy is greater than 15 eV, the tendency for the real part of the spectrum is identical to that corresponding to adsorption by different alkali metals. The imaginary part $\varepsilon_2(\omega)$ as a function of ω for pristine and alkali-metal-adsorbed g-GaN is shown in Fig. 6b. Two narrow peaks located at 6.18 and 10.76 eV, which originate from the transition of N-2p electrons into the s states of the cations, are shifted toward lower energies upon alkali-metal adsorption. Moreover, a high peak arises at 1.22 eV following alkali-metal adsorption.

Figure 7 shows the absorption coefficient and refractive indices for pristine and alkali-metal-adsorbed g-GaN. In Fig. 7a, the absorption edge of pristine g-GaN begins at 2.77 eV; this absorption stems from the excited electron transition from N-2p states located at the top of the

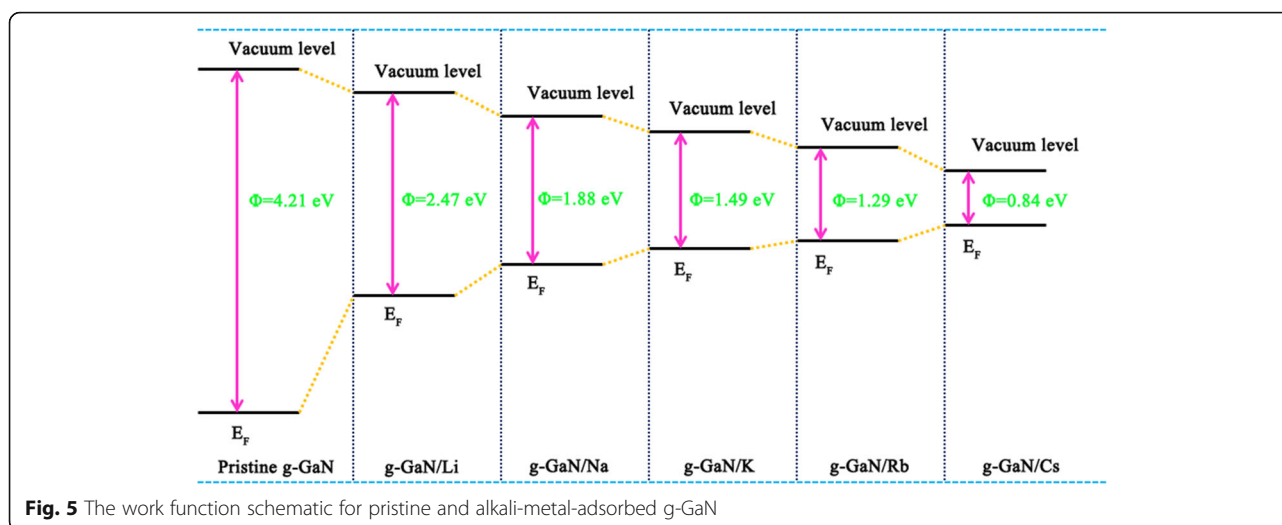

valence band to the empty cation 2 s states. The spectrum of pristine g-GaN shows two peaks located at 6.28 and 10.95 eV; these peaks exhibit a redshift after alkali-metal adsorption. In addition, the intensities the two peaks decrease following alkali-metal adsorption. Moreover, a new peak emerges at 1.61 eV following alkali-metal adsorption, and some miscellaneous peaks appear at energies greater than 12.46 eV in the spectra of K-, Rb-, and Cs-adsorbed g-GaN. These results indicate that the alkali-metal-adsorbed g-GaN materials show a wide range of adjustment in their absorption spectra. Furthermore, the absorption coefficients for pristine and alkali-metal-adsorbed g-GaN are related to the imaginary part and the extinction index, as shown in Figs. 6b and 8c. As shown in Fig. 7b, the values for $n(0)$ are 1.22 (pristine), 1.53 (Li), 1.78 (Na), 1.89 (K),

1.99 (Rb), and 1.99 (Cs). The $n(0)$ values for pristine g-GaN and alkali-metal-adsorbed g-GaN are slightly lower than those obtained for pristine GaN nanowires and alkali-metal-adsorbed GaN nanowires [12]. With increasing photo energy, the refractive index of pristine g-GaN reaches a maximum value of approximately 1.65 at 5.88 eV, whereas the refractive indices of alkali-metal-adsorbed g-GaN reach a maximum value of approximately 1.75–2.25 at 0.7–2 eV. In addition, the refractive indices of pristine g-GaN and alkali-metal-adsorbed g-GaN reach a minimum value of approximately 11.41 eV. Finally, the refractive indices remain unchanged with a value of 0.91 when the photo energy is greater than 15 eV.

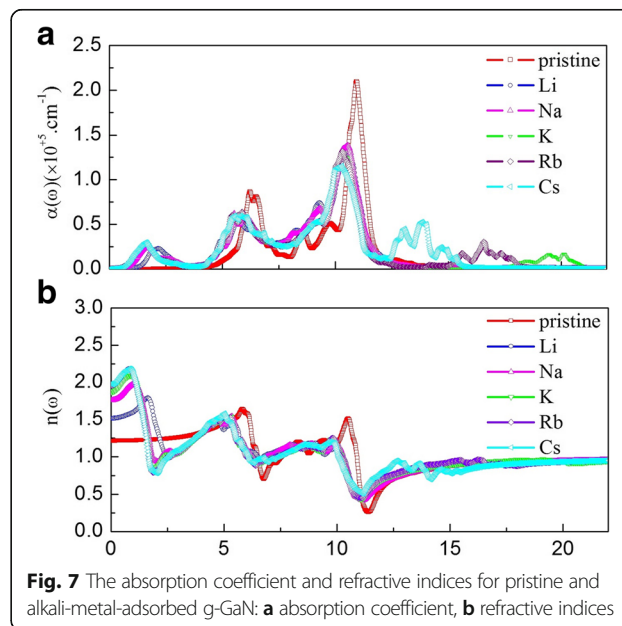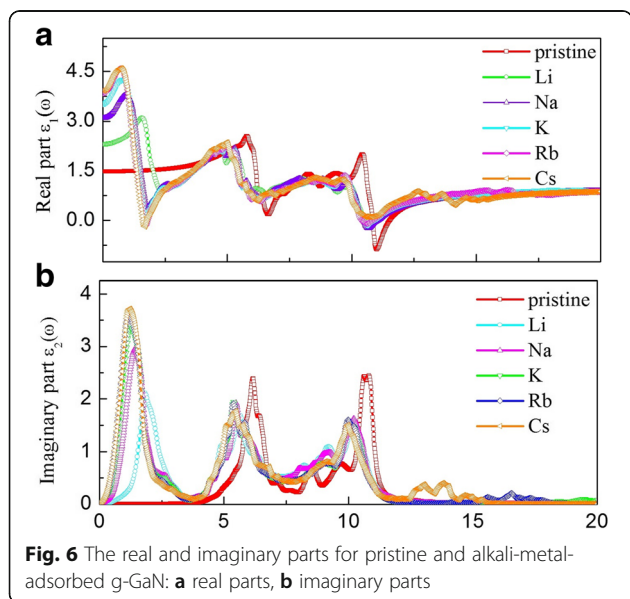

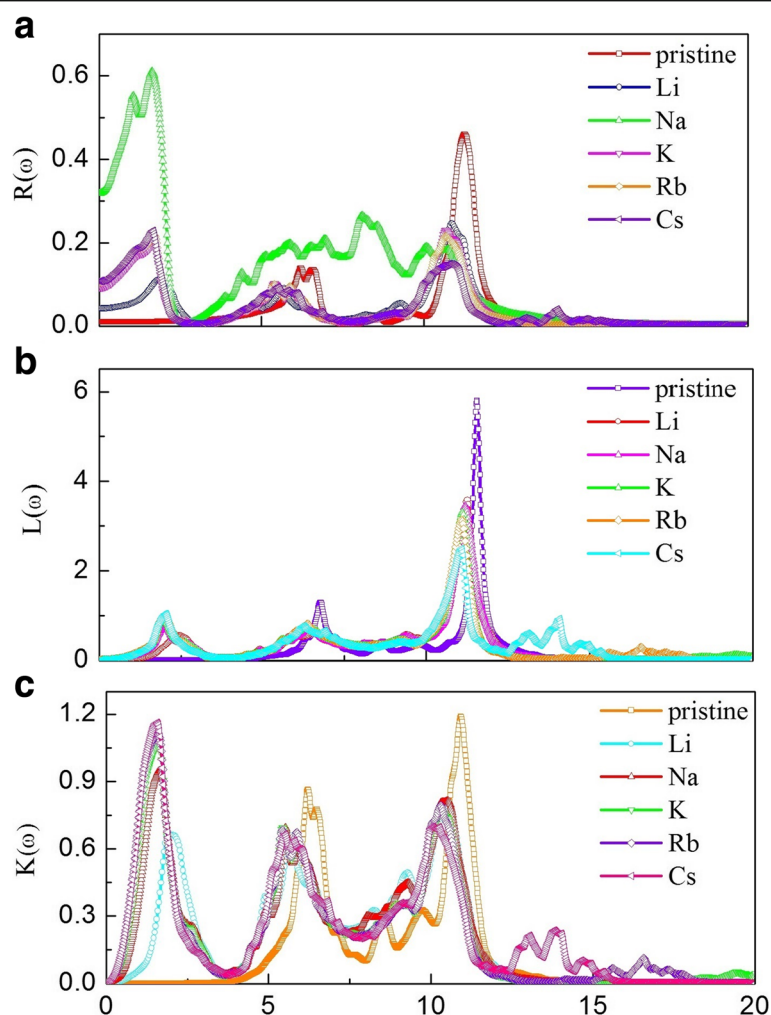


Fig. 8 The reflectivity coefficient, loss energy function, and extinction coefficient for pristine and alkali-metal-adsorbed g-GaN: **a** reflectivity coefficient, **b** loss energy function, **c** extinction coefficient

The reflectivity coefficient $R(\omega)$ for pristine and alkali-metal-adsorbed g-GaN is shown in Fig. 8a. A strong reflection peak is located at 11.3 eV for pristine g-GaN; however, the peak intensity decreases after alkali-metal adsorption. Moreover, a new reflection peak emerges in the low-energy region (0–2.5 eV), which indicates that the reflection spectrum is extended after alkali-metal adsorption. The energy-loss function $L(\omega)$ for pristine and alkali-metal-adsorbed g-GaN is shown in Fig. 8b; the data show that the most prominent peak for pristine g-GaN is located at approximately 11.57 eV, whereas the most prominent peak for alkali-metal-adsorbed g-GaN appears at 11.12 eV. The peak intensity for the alkali-metal-adsorbed g-GaN is lower than that for the pristine g-GaN; thus, the energy loss is slower for electron transmission in alkali-metal-adsorbed g-GaN. In addition, the alkali-metal-adsorbed g-GaN is a stable compound. The extinction coefficient $K(\omega)$ of pristine and

alkali-metal-adsorbed g-GaN is shown in Fig. 8c. The extinction coefficient for the alkali-metal-adsorbed g-GaN is similar to the reflectivity coefficient. Thus, the optical properties of g-GaN can be tuned via the adsorption of alkali-metal atoms, which is useful for the fabrication of optoelectronic devices.

Conclusions

The electronic and optical properties of alkali-metal-adsorbed g-GaN systems were investigated using density functional theory. The results are summarized as follows: (1) all the alkali-metal-adsorbed g-GaN are rather stable with the most stable adsorption site being the T_M site. (2) The adsorption of alkali metal atoms on g-GaN occurs via chemisorption. (3) An n-doping behavior can be found in g-GaN after the adsorption of alkali-metal adatoms. (4) The work function of g-GaN is considerably reduced following alkali-metal adsorption, with the

Cs-adsorbed g-GaN system showing the minimum work function of only 0.84 eV, thus, the Cs adsorbed g-GaN system has potential application in field-emission devices. (5) Alkali-metal adsorption can lead to an increase in the static dielectric constant and extend the absorption spectrum of g-GaN. Consequently, the adsorption of alkali metals can be used to decorate and enlarge the optoelectronic properties of g-GaN, which can be used to produce photoelectric devices.

Abbreviations

2D: Two-dimensional; GGA: Generalized gradient approximation; g-GaN: Graphene-like gallium nitride; PBE: Perdew-Burke-Ernzerhof; PDOS: Partial density of states; TDOS: Total density of states

Funding

This work was supported by the National Natural Science Foundation of China (No.11747032), the Natural Science Basic Research Plan in Shaanxi Province of China (No.2017JQ6065), the Innovation Project of Key Industry Chain in Shaanxi Province (No. 2017ZDCXL-GY-06-01), the Science and Technology Project of Xi'an (No. 2017080CG/RC043(XALG015)), the Science Foundation of Guizhou Science and Technology Department (No. QKHJZ[2015]2150), and the Science Foundation of Guizhou Provincial Education Department (No. QJHKYZ[2016]092). First-principles calculations were carried out on the Chen Qingyun's group clusters at the Southwest University of Science and Technology.

Availability of data and materials

They are all in the main text and figures.

Authors' contributions

ZC and MS design the project. ZC and XW wrote the manuscript. YD, EL, and CS made the theoretical analysis. All the authors discussed the results. All authors read and approved the final manuscript.

Competing interests

The authors declare that they have no competing interests.

Publisher's Note

Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Author details

¹School of Automation and Information Engineering, Xi'an University of Technology, Xi'an 710048, People's Republic of China. ²College of Optoelectronics Technology, Chengdu University of Information Technology, Chengdu 610225, People's Republic of China. ³Department of Radiology, Affiliated Hospital of Yan'an University, Yan'an 716000, People's Republic of China. ⁴State Key Lab of Crystal Materials, Shandong University, Jinan 250100, Shandong, People's Republic of China. ⁵School of Mechanical Engineering, Southeast University, Nanjing, Jiangsu 211189, People's Republic of China. ⁶Institute of High Performance Computing, A*STAR, Singapore 138632, Singapore.

Received: 5 April 2018 Accepted: 29 June 2018

Published online: 11 July 2018

References

1. Strite S, Morkoç H (1992) GaN, AlN, and InN: a review. *J Vac Sci Technol B* 10(4):1237–1266
2. Monemar B (1999) III-V nitrides-important future electronic materials. *J Mater Sci Mater El* 10:227–254
3. Nair RR, Blake P, Grigorenko AN, Novoselov KS, Booth TJ, Stauber T (2008) Fine structure constant defines visual transparency of graphene. *Science* 320:1308–1308
4. Novoselov KS, Geim AK, Morozov SV, Jiang D, Katsnelson MI, Grigorieva IV, Dubonos SV, Firsov AA (2005) Two-dimensional gas of massless dirac fermions in graphene. *Nature* 438:197–200
5. Chhowalla M, Shin HS, Eda G, Li LJ, Loh KP, Zhang H (2013) The chemistry of two-dimensional layered transition metal dichalcogenide nanosheets. *Nat Chem* 5:263–275
6. Wang QH, Kalantarzadeh K, Kis A, Coleman JN, Strano MS (2012) Electronics and optoelectronics of two-dimensional transition metal dichalcogenides. *Nat Nanotechnol* 7:699–712
7. Wan C, Gu X, Feng D, Itoh T, Wang Y, Sasaki H, Yang R (2015) Flexible n-type thermoelectric materials by organic intercalation of layered transition metal dichalcogenide TiS₂. *Nat Mater* 14:622–627
8. Qian X, Liu J, Fu L, Li J (2014) Cheminform abstract: quantum spin hall effect in two-dimensional transition metal dichalcogenides. *Science* 346:1344–1347
9. Reich ES (2014) Phosphorene excites materials scientists. *Nature* 506(7486):19.
10. Xu M, Liang T, Shi M, Chen H (2013) Graphene-like two-dimensional materials. *Chem Rev* 113(5):3766–3798
11. ZYAI B, Wang K, Ghosh RK, Vilá RA, Eichfeld SM, Caldwell JD, Subramanian S (2016) Two-dimensional gallium nitride realized via graphene encapsulation. *Nat Mater* 15(11):1166–1171
12. Cui Z, Li E, Ke X, Zhao T, Yang Y, Ding Y, Qu Y, Xu S (2017) Adsorption of alkali-metal atoms on GaN nanowires photocathode. *Appl Surf Sci* 423:829–835
13. Chan KT, Neaton JB, Cohen ML (2008) First-principles study of metal adatom adsorption on graphene. *Phys Rev B* 77(23):235430
14. Jin KH, Choi SM, Jhi SH (2010) Crossover in the adsorption properties of alkali metals on graphene. *Phys Rev B* 82(3):033414
15. Qiao L, Qu CQ, Zhang HZ, Yu SS, Hu XY, Zhang XM, Zheng WT (2010) Effects of alkali metal adsorption on the structural and field emission properties of graphene. *Diam Relat Mater* 19(11):1377–1381
16. Ding Y, Wang Y (2015) Structural, electronic, and magnetic properties of adatom adsorptions on black and blue phosphorene: a first-principles study. *J Phys Chem C* 119(19):10610–10622
17. Kulish VV, Malyi OI, Persson C, Wu P (2015) Adsorption of metal adatoms on single-layer phosphorene. *Phys Chem Chem Phys* 17(2):992–1000
18. Hu T, Hong J (2015) First-principles study of metal adatom adsorption on black phosphorene. *J Phys Chem C* 119(15):8199–8207
19. Tan C, Yang Q, Meng R, Liang Q, Jiang J, Sun X, Ye H, Chen XP (2016) An AlAs/germanene heterostructure with tunable electronic and optical properties via external electric field and strain. *J Mater Chem C* 4(35):8171–8178
20. Jiang J, Liang Q, Meng R, Yang Q, Tan C, Sun X, Chen X (2017) Exploration of new ferromagnetic, semiconducting and biocompatible Nb₃X₈ (X=Cl, Br or I) monolayers with considerable visible and infrared light absorption. *Nanoscale* 9(9):2992–3001
21. Meng R, Lu X, Ingebrandt S, Chen X (2017) Adsorption of gas molecules on graphene-like ZnO nanosheets: the roles of gas concentration, layer number, and heterolayer. *Adv Mater Interfaces* 4(21):1700647
22. Yang Q, Tan CJ, Meng RS, Jiang JK, Liang QH, Sun X, Yang D, Chen XP (2017) AlN/BP heterostructure photocatalyst for water splitting. *IEEE Electr Device L* 38(1):145–148
23. Cui H, Zheng K, Zhang Y, Ye H, Chen X (2018) Superior selectivity and sensitivity of C₃N sensor in probing toxic gases NO₂ and SO₂. *IEEE Electr Device L* 39(2):284–287
24. Kresse G, Furthmüller J (1996) Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys Rev B Condens Matter* 54(16):11169–11186
25. Kresse G, Furthmüller J (1996) Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput Mater Sci* 6:15–50
26. Perdew JP, Burke K, Ernzerhof M (1996) Generalized gradient approximation made simple. *Phys Rev Lett* 77(18):3865
27. Sun M, Tang W, Ren Q, Wang S, Jin Y, Du Y (2015) First-principles study of the alkali earth metal atoms adsorption on graphene. *Appl Surf Sci* 356:668–673
28. Sun M, Ren Q, Zhao Y, Chou JP, Yu J, Tang W (2017) Electronic and magnetic properties of 4d series transition metal substituted graphene: a first-principles study. *Carbon* 120:265–273
29. Cui Z, Li E (2017) GaN nanocones field emitters with the selenium doping. *Opt Quant Electron* 49(4):146

30. Cui Z, Ke X, Li E, Liu T (2016) Electronic and optical properties of titanium-doped GaN nanowires. *Mater Des* 96:409–415
31. Tang W, Sun M, Yu J, Chou JP (2018) Magnetism in non-metal atoms adsorbed graphene-like gallium nitride monolayers. *Appl Surf Sci* 427:609–612
32. Sun M, Chou JP, Yu J, Tang W (2017) Electronic properties of blue phosphorene/graphene and blue phosphorene/graphene-like gallium nitride heterostructures. *Phys Chem Chem Phys* 19(26):17324
33. Sun M, Chou JP, Ren Q, Zhao Y, Yu J, Tang W (2017) Tunable schottky barrier in van der waals heterostructures of graphene and g-GaN. *Appl Phys Lett* 110(17):192
34. Xia C, Peng Y, Wei S, Jia Y (2013) The feasibility of tunable p-type Mg doping in a GaN monolayer nanosheet. *Acta Mater* 61(20):7720–7725
35. Chen GX, Li HF, Yang X, Wen JQ, Pang Q, Zhang JM (2018) Adsorption of 3d transition metal atoms on graphene-like gallium nitride monolayer: a first-principles study. *Superlattice Microst* 115:108–115
36. Fox AM (2001) *Optical properties of solids Vol 3:3–4* (Oxford university press)
37. Lashgari H, Boochani A, Shekaari A, Solaymani S, Sartipi E, Mendi RT (2016) Electronic and optical properties of 2D graphene-like ZnS: DFT calculations. *Appl Surf Sci* 369:76–81
38. Legesse M, Fagas G, Nolan M (2017) Modifying the band gap and optical properties of germanium nanowires by surface termination. *Appl Surf Sci* 396:1155–1163
39. Cui Z, Wang X, Ding Y, Li M (2018) Exploration work function and optical properties of monolayer SnSe allotropes. *Superlattice Microst* 114:251–258
40. Shahrokhi M, Leonard C (2017) Tuning the band gap and optical spectra of silicon-doped graphene: many-body effects and excitonic states. *J Alloy Comp* 693:1185–1196

Submit your manuscript to a SpringerOpen[®] journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► [springeropen.com](https://www.springeropen.com)